



Cite this: *J. Mater. Chem. A*, 2015, 3, 23426

A multifunctional microporous anionic metal–organic framework for column-chromatographic dye separation and selective detection and adsorption of Cr^{3+}

Shu-Ran Zhang,^a Jing Li,^a Dong-Ying Du,^{*a} Jun-Sheng Qin,^a Shun-Li Li,^b Wen-Wen He,^a Zhong-Min Su^{*a} and Ya-Qian Lan^{*ab}

In this work, a novel microporous anionic metal–organic framework (MOF), $[\text{Zn}(\text{ABTC})_{0.5}(\text{NO}_3)] [(\text{CH}_3)_2\text{NH}_2] \cdot \text{DMA} \cdot 3\text{H}_2\text{O}$ (**NENU-505**; NENU = Northeast Normal University; H_4ABTC = 3,3',5,5'-azobenzenetetracarboxylic acid; DMA = *N,N*-dimethylacetamide), has been rationally synthesized under solvothermal conditions. Single-crystal X-ray analysis reveals that **NENU-505** is a (4,4)-connected 3D network with pts topology. Charge neutrality is achieved by $[(\text{CH}_3)_2\text{NH}_2]^+$ ions. It is noteworthy that **NENU-505** displays high stability in air for more than two months. In particular, the adsorption ability of **NENU-505** toward ionic dyes has been also investigated. According to the UV/vis spectroscopy analysis and the colour variance of **NENU-505**, we found that the cationic dyes could be efficiently adsorbed over a period of time, while the neutral and anionic dyes could not be adsorbed. Therefore, **NENU-505** exhibits selective adsorption toward cationic dyes and can potentially serve as a column-chromatographic filler for the separation of dye molecules. Furthermore, the cationic dyes can be gradually released in the presence of NaCl. More interestingly, when **NENU-505** was immersed in different metal ion DMA solutions, it performs as a rare example of a highly selective and sensitive sensor for Cr^{3+} ions. In connection to this, the probable sensing mechanism was also further investigated in detail in this paper. Remarkably, this is the first MOF to exhibit an excellent ability for the detection and adsorption of Cr^{3+} ions in a convenient, economical, and environmentally friendly manner.

Received 16th September 2015
Accepted 9th October 2015

DOI: 10.1039/c5ta07427d

www.rsc.org/MaterialsA

Introduction

Metal–organic frameworks (MOFs), also known as porous coordination polymers (PCPs), have attracted tremendous attention for their emerging energy- and environment-related applications in numerous areas,¹ including but not limited to, gas storage and separation,² luminescence,³ heterogeneous catalysis⁴ and chemical sensing.⁵ In general, MOFs, as indicated by the name, are crystalline materials constructed by “one-pot” solvothermal or hydrothermal syntheses by judicious selection of the two main interacting components: single metal cations (primary building unit or PBU) or metal clusters (secondary

building unit or SBU) and organic ligands.⁶ MOFs possess diverse topologies with aesthetic beauty through the formation of one, two, or three dimensional extended coordination networks by multiple binding sites of components. Numerous research efforts have mainly been aimed at preparing novel MOFs with structurally fascinating and functional diversification,⁷ and some MOFs are now commercialized. It should be noted that charged MOFs have been widely explored as an appealing subclass due to the fact that the framework charge (*i.e.*, cationic, neutral, or anionic) of MOF materials has a profound effect on their functionalities.⁸ Generally speaking, the charge-balancing cations/anions usually occupy the void space, potentially allowing the capture and separation of other anions/cations through ion exchange.⁹

It has been extensively recognized that dyes have found an increasingly wide utilization in many industrial fields, including paper, printing, plastics, textiles, cosmetics, pharmaceuticals and so on.¹⁰ However, the toxicities of several dyes have brought about a significant threat to the aqueous environment and caused serious consequences, such as aesthetic pollution, even carcinogenicity and perturbation to aquatic life.¹¹ Therefore, in daily life, technologies with high efficiency

^aInstitute of Functional Material Chemistry, Faculty of Chemistry, Northeast Normal University, Changchun 130024, Jilin, People's Republic of China. E-mail: zmsu@nenu.edu.cn; yqlan@nenu.edu.cn

^bJiangsu Key Laboratory of Biofunctional Materials, School of Chemistry and Materials Science, Nanjing Normal University, Nanjing 210023, Jiangsu, People's Republic of China

† Electronic supplementary information (ESI) available: TGA, XPRD patterns, IR, UV, EDS and XPS data and additional figures for **NENU-505**. CCDC 1412229. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c5ta07427d

and low consumption to reduce the harmful pollutant contents of printing and dyeing are urgently required concerning a clean environment and human health. Nevertheless, most dyestuffs are difficult to degrade because of their stability to light and oxidants.¹² Recently, MOFs have been also used for adsorbing or separating dye molecules, and in most cases, dye removal depends on the size-exclusion effect.¹³ Lan and co-workers have reported a series of mesoporous MOFs with a rare corundum topology and tunable cage sizes which was employed as a column-chromatographic filler for the separation of bulk dye molecules by the existence of large cages.¹⁴ To the best of our knowledge, a majority of dyes is charged and could prefer to accommodate in the channels of MOFs with opposite charges. Bearing this in mind, our group has constructed a novel anionic framework with a primitive centered cubic (pcu) topology, which exhibited selective absorption ability towards cationic dyes.¹⁵ Nowadays, it remains a labor-intensive endeavor to synthesize new families of charged MOF materials which can be used to adsorb/separate dyes by virtue of their ionic selectivity.¹⁶

Chromium is widely used in a large amount of industrial processes such as tanning, paint manufacturing, metal processing, electroplating, leather, steel fabrication and agricultural runoff.¹⁷ Chromium is also a trace element necessary for humans and animals. Chromium deficiency can cause atherosclerosis and significantly increase the risk of diabetes and cardiovascular diseases associated with other complications.¹⁸ However, one of its cationic forms, trivalent chromium (Cr^{3+}), has a great influence on the human body and biological environment. An excess of Cr^{3+} can be harmful to human health, leading to deformity. Besides, Cr^{3+} in water bodies can be adsorbed on solid substances and present in sediments.¹⁹ If there is too much chromium in the soil, it will inhibit nitrification of organic matter and make chromium accumulate in plants. The main source of anthropogenic pollution is the discharge of industrial waste gas and waste water containing chromium.²⁰ Chromium residue (chromium-containing solid waste) has become an important environmental issue of chromium pollution. The inappropriate treatment of industrial effluents containing chromium can result in the contamination of natural water sources, eventually threatening human health.²¹ Therefore, there is an urgent need to develop an effective solution that is capable of detecting Cr^{3+} . As far as we know, considerable efforts have been focused on the detection of Zn^{2+} , Mg^{2+} , Cu^{2+} , Fe^{3+} , Ag^{+} and other ions based on MOFs,²² nevertheless, rarely reports have been devoted to the development of sensing and adsorption of Cr^{3+} . In this regard, a fast and efficient sensing approach to probe Cr^{3+} is very promising and significant, particularly with the realization of human health and environment beautification.

Herein, we report a new microporous anionic MOF $[\text{Zn}(\text{ABTC})_{0.5}(\text{NO}_3)][(\text{CH}_3)_2\text{NH}_2]\cdot\text{DMA}\cdot 3\text{H}_2\text{O}$ (**NENU-505**), synthesized by the solvothermal reaction of $\text{Zn}(\text{NO}_3)_2\cdot 6\text{H}_2\text{O}$ and H_4ABTC . It should be noted that **NENU-505** can still maintain its integrated framework in air for more than two months. Meanwhile, **NENU-505** can selectively adsorb cationic dye molecules relative to neutral and anionic molecules because of its anionic framework which makes it a column-

chromatographic filler for adsorption and separation of dyes. Furthermore, **NENU-505** can be utilized as a probe for selectively sensing and adsorbing highly toxic heavy metal Cr^{3+} . This is the first report on an anionic MOF that exhibits convenient, cost-effective, and environmentally friendly properties in the detection and adsorption of Cr^{3+} . However, it is still a long and tortuous procedure to synthesize innovative species of MOF materials for highly selective detection of heavy metal ions.

Results and discussion

A solvothermal reaction of $\text{Zn}(\text{NO}_3)_2\cdot 6\text{H}_2\text{O}$ and H_4ABTC in DMA yields yellow rhombus block crystals of **NENU-505**. The formula of **NENU-505** $[\text{Zn}(\text{ABTC})_{0.5}(\text{NO}_3)][(\text{CH}_3)_2\text{NH}_2]\cdot\text{DMA}\cdot 3\text{H}_2\text{O}$ was elucidated by taking single-crystal X-ray diffraction studies, thermogravimetric analysis (TGA; Fig. S1†), elemental analysis, and charge-balance into consideration. Single-crystal X-ray analysis reveals that **NENU-505** crystallizes in the monoclinic space group $C2/c$ (Table S1†). The asymmetric unit of **NENU-505** contains a Zn^{2+} , a type of ligand fragment, a coordinated NO_3^- and an isolated $[(\text{CH}_3)_2\text{NH}_2]^+$. The Zn atom is four coordinated by three carboxylate oxygen atoms from three ligands and an oxygen atom from coordinated NO_3^- and exhibits a distorted-tetrahedral geometry (Fig. 1a). The Zn–O bond lengths are all within the normal ranges (Table S2†). The adjacent two Zn atoms are connected to each other by one NO_3^- and one H_4ABTC ligand to give rise to a binuclear zinc cluster $[\text{Zn}_2(\text{CO}_2)_4(\text{NO}_3)]$. The ligand unit links the $[\text{Zn}_2(\text{CO}_2)_4(\text{NO}_3)]$ cluster to form an infinite 3D framework. Simultaneously, one binuclear zinc cluster connects four H_4ABTC ligands (Fig. S2a†), in

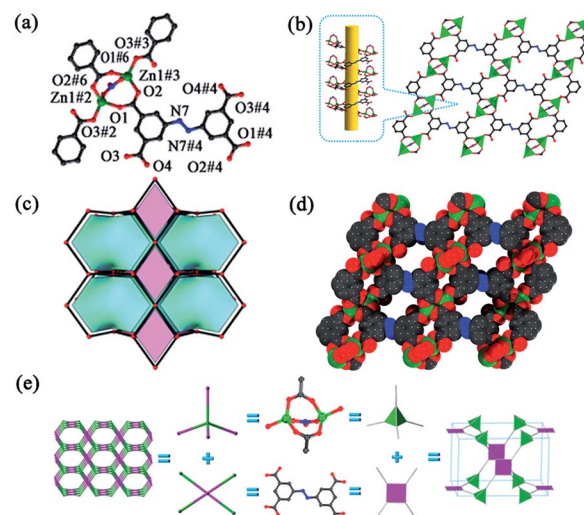


Fig. 1 (a) Coordination environments of $\text{Zn}(\text{II})$ in **NENU-505**. Symmetry code: #1 $x, -y, z + 1/2$; #2 $-x, -y, -z$; #3 $x, -y, z - 1/2$; #4 $-x + 1/2, -y + 1/2, -z$; #5 $-x, y, -z + 1/2$; #6 $-x, y, -z - 1/2$. (b) Representations of the helices in the channel. (c) The (4,4)-connected augmented net as a natural tiling. (d) Ball-and-stick and space-filling representations of its packing arrangement of the 3D structure in **NENU-505**. (e) Ball-and-stick and polyhedral view of the (4,4)-connected topology network in **NENU-505**. All the hydrogen atoms are omitted for clarity.

turn, one H_4ABTC ligand coordinates to four binuclear zinc clusters (Fig. S2b†) to form a pore with an approximate size of $10 \times 9.8 \text{ \AA}^2$ along the b axis (Fig. 1b and d), thus suggesting a microporous characteristic of **NENU-505**. A more interesting feature here is that these channels are spiral-shaped (Fig. 1b). Then from the topological analysis, each $[Zn_2(CO_2)_4(NO_3)]$ cluster acts as a 4-connected node and each metalloligand unit is considered as a 4-connected node (Fig. 1c and e), which generates a (4,4)-connected 3D network with pts topology (Schläfli symbol of $(4^2 \cdot 8^4)$).²³ Overall, the framework of **NENU-505** is anionic, $[(CH_3)_2NH_2]^+$ ions located in the channel help to balance the charge (Fig. S3†). The protonated $[(CH_3)_2NH_2]^+$ ions in **NENU-505** originate from the decarbonylation of dimethylamine.²⁴ From the single-crystal X-ray diffraction studies and the charge-balance consideration, there is one $[(CH_3)_2NH_2]^+$ ion per formula unit. The experimental X-ray powder diffraction (XRPD) patterns of both simulated and the as-synthesized **NENU-505** match well in key positions, thus indicating its phase purity (Fig. S4†). **NENU-505** can just maintain its stability in water for several hours as demonstrated by XRPD (Fig. S4†), and then turn into amorphous. Notably, under ambient conditions, that is to say, exposure to air for more than two months, no major changes to either the external appearance or to the XRPD

patterns of **NENU-505** were observed, confirming the extreme stability of the framework (Fig. S5†). To ensure the structural integrity and stability of **NENU-505** exposed in air after two months, we have presented its optical image taken by using a fluorescence microscope equipped with a CCD camera (Fig. S5†).

It is extremely important to remove dyes from effluents before discharging them into natural water bodies from an environmental point of view since dyes have been widely employed in several industries.²⁵ Until now, many methods have been utilized in order to remove dyes from the environment. Significantly, this involves the adsorption approach without chemical degradation which is extremely attractive in virtue of its effectiveness, efficiency and economy.²⁶ Owing to its simple preparation, easy acquisition of raw materials and its porous anionic framework nature, **NENU-505** was explored as a column-chromatographic filler for adsorption and separation of dyes based on ionic interactions between the cationic dyes and anionic framework. **NENU-505** does not require any activation process compared with other reported MOFs for dye sorption.²⁷ To evaluate whether **NENU-505** has the absorption ability to separate dye molecules, we selected freshly prepared **NENU-505** to capture dyes from solutions in DMA. We carefully

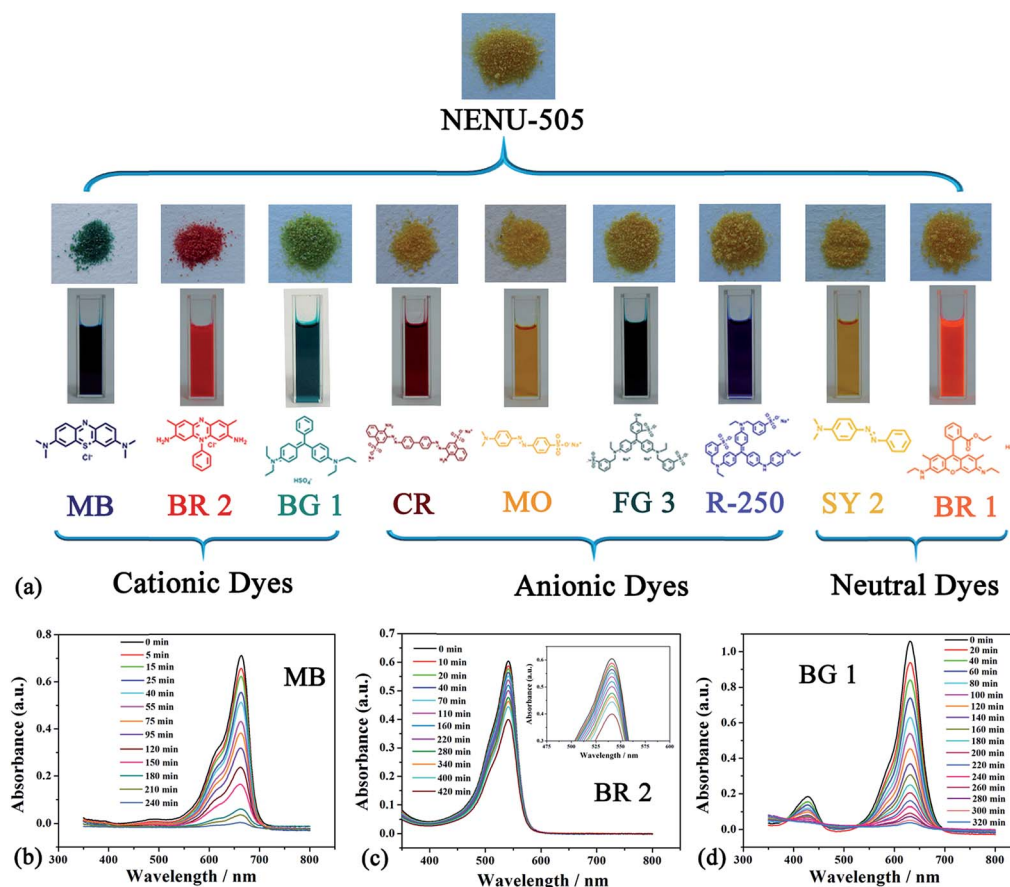


Fig. 2 (top a) Schematic illustration of the dye molecules employed in the dye-absorption experiments and photographs of the corresponding colour change of crystals after immersion into the solutions of the dyes for a period of time. (bottom) UV/vis spectra of DMA solutions of (b) MB, (c) BR 2, and (d) BG 1 with freshly prepared **NENU-505**, respectively. Inset: the enlargements of the corresponding UV/vis absorption.

selected nine dye molecules with different shapes, sizes and charges, including cationic dyes (methylene blue (MB), basic red 2 (BR 2), and basic green 1 (BG 1)), anionic dyes (Congo red (CR), methyl orange (MO), food green 3 (FG 3), and R-250), and neutral dyes (solvent yellow 2 (SY) and basic red 1 (BR 1)), in which some perhaps would be adsorbed. Typically, when freshly prepared **NENU-505** (100 mg) was soaked in DMA solutions of different kinds of dyes (10 mL, 1.0 mmol), the cationic dyes (MB, BR 2, and BG 1) could be efficiently adsorbed over a period of time and the yellow crystals gradually became coloured, while the neutral and anionic dyes could not be adsorbed (Fig. 2a). Among these dyes, for MO and SY 2, the main reason for non-adsorbing is that the charge does not match, as well as larger shapes and sizes of CR, FG 3, R-250 and BR 1. Meanwhile, the capability of **NENU-505** to adsorb the three cationic dyes from solutions of DMA was quantitatively determined through UV/vis spectroscopy analysis (Fig. 2b–d), which indicated that the concentration of cationic dyes in DMA significantly decreased with the passage of time. At the same instant, spectroscopic investigations of the supernatants also showed that **NENU-505** could completely and rapidly adsorb MB. The adsorption capacity of **NENU-505** at room temperature was 33.5 mg g^{-1} for MB, 4.5 mg g^{-1} for BR 2, and 17.6 mg g^{-1} for BG 1. The adsorptivity of **NENU-505** for MB is higher than that of some other materials reported until now (Table S3†). The distinction in the shape and size of the three cationic dyes may result in the difference of adsorption quantity. According to the structure, MB is linear and BR and BG 1 are planar, which make MB relatively smaller than other two cationic dyes. In addition, no major changes to either the external appearance or to the XRPD and IR patterns of **NENU-505** were detected after the successful exchange of cationic dyes, as proved by the XRPD and IR profiles (Fig. S6 and S7†).

The above results inspired us that **NENU-505** may be a potential adsorbent for the removal of cationic dyes from

effluents. Therefore, we prepared a chromatography column filled with **NENU-505** and DMA solutions prepared by mixing two different types of dyes MB and BR 1 (1 : 1, 1.0 mmol) were passed through the column-chromatography filler. As displayed in Fig. 3, the colour of the column finally became blackish green, which indicated that cationic dye MB was adsorbed inside **NENU-505** for a longer time along with the DMA stream. In the meantime, neutral and unadsorbed dye BR 1 was rapidly transported through the column. Thus the two kinds of dyes MB and BR 1 can be successfully and quickly separated by passing them through the MOF-filled column, which was not only observed by the naked eye but also evaluated through UV/vis spectroscopy of the effluent (Fig. 4). The continuing decrease of the characteristic wavelength for MB reveals its successful absorbance, while the unchanged peak of BR 1 suggests its exclusion by **NENU-505**. Additionally, we have also monitored UV/vis spectroscopy of other dye mixtures in order to ensure the capability of **NENU-505** to adsorb cationic dyes from the effluent, which is indicative of its generality (Fig. S8 and S9†). Moreover, we also calculated the adsorption capacity of **NENU-505** for every dye in the mixture dye (Table S4†). The adsorption capacity is almost the same as the single component dye.

To verify that the kinetic reason for selective absorption toward cationic dyes is ionic interactions between the anionic framework and cationic dye, dye releasing experiments were also carried out in a saturated solution of NaCl in DMA and pure DMA, respectively. **NENU-505** was first soaked in a DMA solution of MB for a period of time to make them saturated. Then 15 mg of the saturated **MB@NENU-505** was added to a 3 mL saturated solution of NaCl in DMA and pure DMA, respectively.²⁸ UV/vis spectra were monitored at different time intervals. The results indicate that MB in **MB@NENU-505** can be gradually released in the presence of NaCl (Fig. 5a), whereas the dye molecules are scarcely released in DMA without NaCl (Fig. 5b). Moreover, it further strengthens the evidence that MB is released *via* the ion exchange process with NaCl acting as a trigger. UV/vis spectra of **BR 2@NENU-505** and **BG 1@NENU-505** were also recorded both in the saturated solution of NaCl in DMA and pure DMA (Fig. S10 and S11†). Owing to the shape and

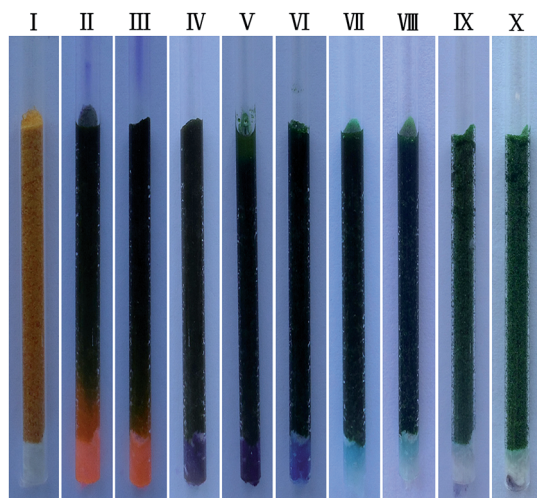


Fig. 3 Photographic records of the **NENU-505**-filled column-chromatographic separation process for MB and BR 1 dyes, in which (I) **NENU-505**-filled column, (II–IX) separation process with the gradual color change, and (X) complete separation with only MB adsorbed.

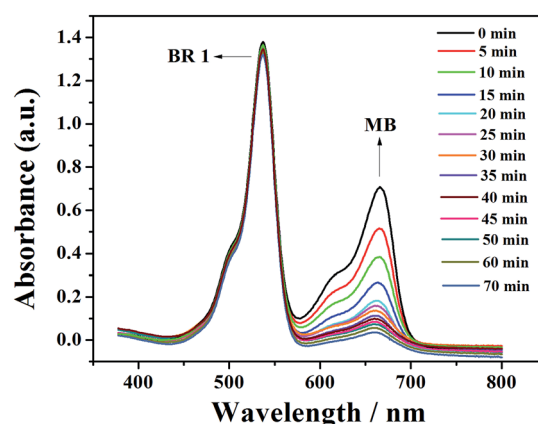


Fig. 4 UV/vis spectra of the DMA solution of mixed MB and BR 1 with **NENU-505**.

size of the three dyes, the release quantity and rate of different types of cationic dyes are different within 420 min. The release percentage is approximately 14.1% for MB, 6.2% for BR 2, and 9.4% for BG 1 within 420 min, respectively. Based on these considerations, we can safely speculate that selective absorption is ascribed to the ionic interaction of the dyes with the anionic framework. The experimental results make it possible that **NENU-505** can be utilized to separate dyes with similar sizes but opposite charges. For the sake of confirming the regeneration and cyclicity of **NENU-505** toward MB, UV/vis spectroscopy analysis was carried out on a solution of MB in DMA after adsorption experiments with **NENU-505**, as well as the MB released (desorption) from **MB@NENU-505** by taking advantage of a saturated solution of NaCl in DMA after six adsorption-desorption cycles (Fig. S12a†). Apart from that, the corresponding removal and regeneration percentages were also calculated (Fig. S12b†). The XRPD patterns further verify that the framework is retained after cycle 6 (Fig. S13†). These results manifested that the dye adsorption and release is a reversible process and **NENU-505** is reusable as an excellent and effective adsorbent.

The existence of $[(CH_3)_2NH_2]^+$ cations and several carboxylate oxygen atoms on the pore surface prompted us to examine the potential of **NENU-505** for the sensing of metal ions by immersing **NENU-505** in DMA solutions containing single

coloured metal ions (Fe^{3+} , Co^{2+} , Ni^{2+} , Cu^{2+} , Fe^{2+} and Cr^{3+} ; 0.01 M), respectively. Owing to the fact that the peak positions of XRPD and IR curves for samples immersed in different metal ions essentially remain unchanged (Fig. S14 and S15†), we can speculate that the basic frameworks in the compounds remained intact after immersion in different metal ions. Interestingly, the samples exhibit an obvious change of solid colour compared to the original one (Fig. 6). It is noticeable that the colour has become bottle green after soaking in DMA solutions containing Cr^{3+} for 48 h ($Cr^{3+}@NENU-505$, 0.01 M), while the colours of other metal ions did not change. Inductively Coupled Plasma (ICP) analysis of resulting samples indicated that **NENU-505** has encapsulated 4.655% Cr^{3+} , which is much higher compared to the other metal ions (Fig. 7). Besides that, the corresponding energy dispersive spectroscopy (EDS) also verified the encapsulation of Cr^{3+} in **NENU-505** (Fig. S16†). To understand the mechanism of the selective capture of Cr^{3+} , we investigated the UV/vis spectra of solid **NENU-505** and $Cr^{3+}@NENU-505$ (Fig. S17†). There is a new band in the UV/vis spectra of $Cr^{3+}@NENU-505$ at 580 nm in addition to the band at 358 nm as observed in **NENU-505**. This may be ascribed to the coordination of Cr^{3+} with the carboxylate oxygen atoms of **NENU-505** through d-d transition. In other words, Cr^{3+} ions were adsorbed on the carboxylate groups. It is widely acknowledged that the flexible geometry of Cr^{3+} is a result of the fact that it can exist in a variety of coordination environments. As shown

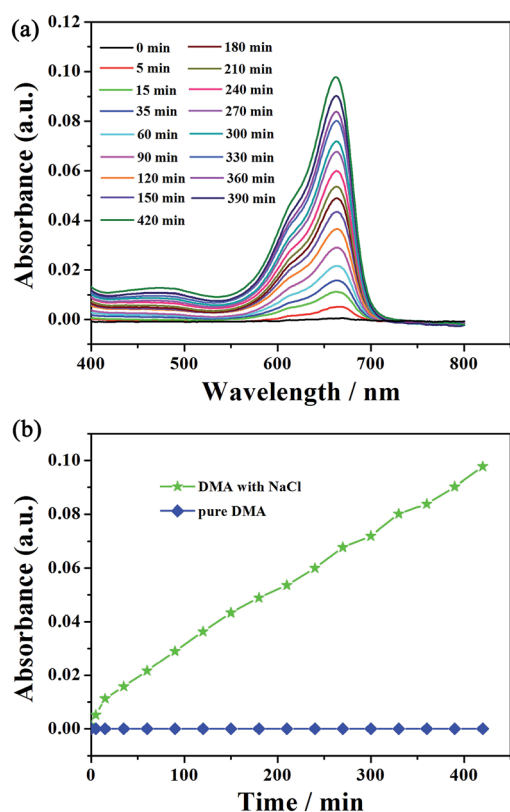


Fig. 5 (a) The MB released from **MB@NENU-505** in a saturated solution of NaCl in DMA monitored by UV absorption. (b) The release-rate comparison of MB from **MB@NENU-505** in a saturated solution of NaCl in DMA (green) and pure DMA (blue).

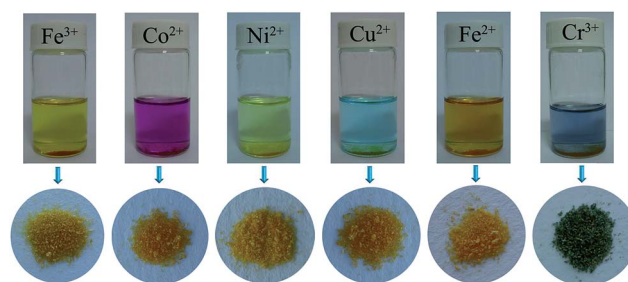


Fig. 6 The photographs of **NENU-505** in 10 mL DMA solutions containing single coloured metal ions (Fe^{3+} , Co^{2+} , Ni^{2+} , Cu^{2+} , Fe^{2+} , and Cr^{3+} ; 0.01 M), respectively.

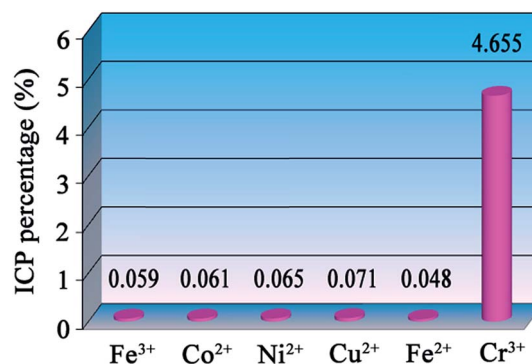


Fig. 7 The ICP percentage of different metal ions encapsulated by **NENU-505**.

in the shaded parts (Fig. S14[†]), for instance, the diffraction intensities corresponding to (1 1 1), (2 0 2), (3 1 $\bar{1}$), (4 0 2), (5 1 0), (1 1 $\bar{4}$), (3 1 3) and (1 1 4) crystallographic planes at 13.16°, 14.08°, 14.84° (shadow 1, Fig. S14[†]), 19.3°, 20.2° (shadow 2, Fig. S14[†]), 22.6°, 23.7° and 24.5° (shadow 3, Fig. S14[†]), respectively, in 2 θ of Cr³⁺@NENU-505 are slightly different compared to simulated NENU-505. In addition, the peak intensities of the IR curve for Cr³⁺@NENU-505 at 1018, 779 and 727 cm⁻¹ (shadow 1 and 2, Fig. S15[†]) are relatively weaker than those of NENU-505. Generally speaking, the peak intensity changes of a few peaks in the XRPD and IR pattern of Cr³⁺@NENU-505 are primarily due to structural reorganization after encapsulation of Cr³⁺. In order to further identify whether Cr³⁺ turn into more nocuous Cr⁶⁺ after encapsulation or not, the X-ray photoelectron spectrometry (XPS) spectrum of Cr³⁺@NENU-505 was monitored (Fig. S18[†]). In the XPS spectrum, there is a pair of peaks at 587.1 and 577.4 eV, which can be ascribed to Cr³⁺ 2p_{1/2} and Cr³⁺ 2p_{3/2}, respectively,²⁹ which indicate that the valence state of chromium does not change. The XPS spectrum also further confirmed the interaction between Cr³⁺ and the uncoordinated carboxylate oxygen atoms. Subsequently, in order to further explore its extraction capacity in multi-element solutions, 50 mg of NENU-505 is immersed in 10 mL DMA solutions containing three equal concentrations of each metal ion (1: Fe²⁺, Cu²⁺ and Cr³⁺; 2: Cu²⁺, Ni²⁺ and Cr³⁺; 3: Cu²⁺, Co²⁺ and Cr³⁺; 4: Ni²⁺, Co²⁺ and Cr³⁺, 0.01 M) for 48 h at room temperature. The colour of NENU-505 has still become bottle green because of adsorbing Cr³⁺ (Fig. S19[†]). The ICP percentage of Cr³⁺ encapsulated by NENU-505 is listed in Table S5.[†] The ICP percentage of Cr³⁺ encapsulated by NENU-505 in multi-element solutions is relatively smaller than that in single metal solutions (4.655%). We speculate that the possible factor that affects separation is the interaction between other metal ions and uncoordinated carboxylate oxygen atoms of NENU-505, giving rise to a competition with Cr³⁺. Therefore, NENU-505 could be applied as a chemical sensor for Cr³⁺ with high sensitivity in systems with complicated components in a convenient, economical, and environmentally friendly manner.

Conclusions

In summary, we have successfully constructed a microporous anionic MOF NENU-505 with a (4,4)-connected pts topology. NENU-505 is extremely stable in air for more than two months. Owing to its anionic framework, NENU-505 can not only be used for selective adsorption and separation of cationic dye molecules but also can be used as a column-chromatography filler for separating dye molecules. Moreover, the cationic dyes could be gradually released in the presence of NaCl, illustrating that the absorption perhaps results from the ionic interaction between the anionic framework and the cationic dyes. And the process of the dye uptake and release is reversible, which suggested that NENU-505 is reusable as a prominent and effective adsorbent. In particular, for the first time, an anionic MOF NENU-505 has been exploited for selectively sensing and adsorbing Cr³⁺ in a high efficiency and low consumption mode due to the presence of [(CH₃)₂NH₂]⁺ cations and carboxyl

groups. The present research has opened up a promising approach to design and prepare MOF-based multifunctional materials, which will probably be useful under more realistic conditions in the future. Considering that the anionic frameworks in the MOF could facilitate targeted fabrication of smart materials with versatile properties, many researchers look forward to synthesizing and exploring novel charged MOFs, research studies on which are currently underway.

Experimental

Materials and measurements

Chemicals were obtained from commercial sources and were used without further purification. X-ray powder diffraction (XRPD) was performed on a Siemens D5005 diffractometer with Cu-K α (λ = 1.5418 Å) radiation in the range of 3–60° at 293 K. Elemental microanalyses (C, H and N) were performed on a Perkin-Elmer 240C elemental analyzer. Cr and other cations were determined with a Plasma-SPEC(I) ICP atomic emission spectrometer. IR spectra were recorded in the range 4000–400 cm⁻¹ on an Alpha Centauri FT/IR spectrophotometer using KBr pellets. Thermogravimetric analysis (TGA) was performed on a Perkin-Elmer TG-7 analyzer heated from 50 °C to 1000 °C at a ramp rate of 10 °C min⁻¹ under nitrogen. The UV/vis absorption spectra were examined on a Shimadzu UV-2550 spectrophotometer in the wavelength range of 300–800 nm. Energy dispersive X-ray spectroscopy (EDS) was performed with a XL30 ESEM FEG microscope. X-ray photoelectron spectrometry (XPS) was performed on a thermo ECSALAB 250 spectrometer with an Al K α (1486.6 eV) achromatic X-ray source running at 15 kV. The XPS binding energy (BE) was internally referenced to the aliphatic C(1s) peak (BE, 284.6 eV).

Synthesis of [Zn(ABTC)_{0.5}(NO₃)][[(CH₃)₂NH₂] \cdot DMA \cdot 3H₂O (NENU-505)

A mixture of H₄ABTC (0.01 g, 0.03 mmol), Zn(NO₃)₂ \cdot 6H₂O (0.19 g, 0.64 mmol), DMA (5 mL), H₂O (3 mL) and three drops of HCl (6 mol L⁻¹) was sealed in a Teflon-lined stainless steel container and heated in an autoclave at 110 °C for 4 days. After the autoclave was cooled to room temperature, yellow crystals were obtained and isolated by washing with DMA and dried at room temperature. Yield: 58% based on H₄ABTC. Elemental microanalysis: anal. calc. for C₁₄H₂₆N_{3.5}O_{9.5}Zn (460.18): C, 36.54; H, 5.65; N, 10.66. Found: C, 36.96; H, 5.74; N, 11.21%. IR (KBr, cm⁻¹, Fig. S7[†]): 3079 (m), 2937 (m), 2487 (w), 1634 (s), 1448 (s), 1357 (s), 1244 (s), 1188 (m), 1018 (m), 961 (w), 928 (w), 779 (s), 672 (w), 593 (w), 473 (m).

X-ray crystallography

Single crystal X-ray diffraction data in this work were recorded on a Bruker APEXII CCD diffractometer with graphite-monochromated Mo K α radiation (λ = 0.71069 Å) at 293 K. Absorption corrections were applied using the multi-scan technique. All the structures were solved by direct methods using SHELXS-97 (ref. 30a) and refined by full-matrix least-squares techniques using the SHELXL-97 program^{30b} within WINGX.^{30c} Non-hydrogen

atoms were refined with anisotropic temperature parameters. The SQUEEZE program implemented in PLATON^{30d} was used to remove the electron densities of the compounds. Thus, all the electron densities from free solvent molecules have been “squeezed” out. The detailed crystallographic data and structure refinement parameters are summarized in Table S1.†

Experimental details for dye adsorption, release and separation

Dye adsorption. Freshly prepared NENU-505 (100 mg) was soaked in DMA solutions of cationic dyes (methylene blue (MB), basic red 2 (BR 2), and basic green 1 (BG 1)), anionic dyes (Congo red (CR), methyl orange (MO), food green 3 (FG 3), and R-250), and neutral dyes (solvent yellow 2 (SY) and basic red 1 (BR 1)), respectively. After two days of soaking, the samples were washed with DMA.

Dye release. The NENU-505 samples loaded with MB, BR 2, and BG 1 (15 mg) were transferred into pure DMA and a saturated solution of NaCl in DMA (3 mL) in cuvettes (4 mL), respectively. UV/vis spectra were employed to monitor the absorption ability and release process of NENU-505 after certain time intervals.

Column-chromatographic dye separation. The sealed bottom of the NMR sample tube (\varnothing 5 mm, 180 mm) was cut off from middle and NENU-505 was filled in the NMR sample tube (80 mm) as a chromatographic column. NENU-505 does not need any activation procedure. First, the DMA solutions of mixed MB/BR 1 (1 : 1, 1.0 mmol) were passed through the chromatographic column at the room temperature. Then pure DMA was passed through the chromatographic column. The time of completing the whole separation is probably 30 min. The UV-vis spectra of effluents were examined to confirm the separation capability.

Experimental details for sensing Cr³⁺

Firstly, 50 mg of NENU-505 is immersed in 10 mL DMA solutions containing single coloured metal ions (Fe³⁺, Co²⁺, Ni²⁺, Cu²⁺, Fe²⁺ and Cr³⁺; 0.01 M) for 48 h at room temperature. Then so as to further investigate its extraction capacity in multi-element solutions, 50 mg of NENU-505 is immersed in 10 mL DMA solutions containing three equal concentrations of each metal ion (1: Fe²⁺, Cu²⁺ and Cr³⁺; 2: Cu²⁺, Ni²⁺ and Cr³⁺; 3: Cu²⁺, Co²⁺ and Cr³⁺; 4: Ni²⁺, Co²⁺ and Cr³⁺; 0.01 M) for 48 h at room temperature. The samples were washed with DMA after soaking.

Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (No. 21371099 and 21401021), the China Postdoctoral Science Foundation (No. 2014M551154 and 2015T80284), the Science and Technology Development Planning of Jilin Province (No. 20140520089JH and 20140203006GX), the Jiangsu Specially-Appointed Professor, the NSF of Jiangsu Province of China (No. BK20130043), the Priority Academic Program Development of Jiangsu Higher Education Institutions, the Foundation of Jiangsu Collaborative

Innovation Center of Biomedical Functional Materials, and the Fundamental Research Funds for the Central Universities (No. 14QNJJ013).

Notes and references

- (a) H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, *Science*, 2013, **341**, 1230444; (b) A. G. Slater and A. I. Cooper, *Science*, 2015, **348**, 8075; (c) Q.-L. Zhu and Q. Xu, *Chem. Soc. Rev.*, 2014, **43**, 5468; (d) W. Lu, Z. Wei, Z.-Y. Gu, T.-F. Liu, J. Park, J. Park, J. Tian, M. Zhang, Q. Zhang, T. Gentle III, M. Bosch and H.-C. Zhou, *Chem. Soc. Rev.*, 2014, **43**, 5561; (e) R. J. Kuppler, D. J. Timmons, Q.-R. Fang, J.-R. Li, T. A. Makal, M. D. Young, D. Yuan, D. Zhao, W. Zhuang and H.-C. Zhou, *Coord. Chem. Rev.*, 2009, **253**, 3042; (f) J. R. Long and O. M. Yaghi, *Chem. Soc. Rev.*, 2009, **38**, 121; (g) S.-L. Li and Q. Xu, *Energy Environ. Sci.*, 2013, **6**, 1656.
- (a) L. J. Murray, M. Dincă and J. R. Long, *Chem. Soc. Rev.*, 2009, **38**, 1294; (b) T. A. Makal, J.-R. Li, W. Lu and H.-C. Zhou, *Chem. Soc. Rev.*, 2012, **41**, 7761; (c) M. P. Suh, H. J. Park, T. K. Prasad and D.-W. Lim, *Chem. Rev.*, 2012, **112**, 782; (d) K. Sumida, D. L. Rogow, J. A. Mason, T. M. McDonald, E. D. Bloch, Z. R. Herm, T.-H. Bae and J. R. Long, *Chem. Rev.*, 2012, **112**, 724; (e) J.-R. Li, J. Sculley and H.-C. Zhou, *Chem. Rev.*, 2012, **112**, 869; (f) H. Wu, Q. Gong, D. H. Olson and J. Li, *Chem. Rev.*, 2012, **112**, 836; (g) P. Nugent, Y. Belmabkhout, S. D. Burd, A. J. Cairns, R. Luebke, K. Forrest, T. Pham, S. Ma, B. Space, L. Wojtas, M. Eddaoudi and M. J. Zaworotko, *Nature*, 2013, **495**, 80; (h) T. Grancha, J. Ferrando-Soria, H.-C. Zhou, J. Gascon, B. Seoane, J. Pasán, O. Fabelo, M. Julve and E. Pardo, *Angew. Chem., Int. Ed.*, 2015, **54**, 6521; (i) J.-S. Qin, D.-Y. Du, W.-L. Li, J.-P. Zhang, S.-L. Li, Z.-M. Su, X.-L. Wang, Q. Xu, K.-Z. Shao and Y.-Q. Lan, *Chem. Sci.*, 2012, **3**, 2114; (j) P. Shen, W.-W. He, D.-Y. Du, H.-L. Jiang, S.-L. Li, Z.-L. Lang, Z.-M. Su, Q. Fu and Y.-Q. Lan, *Chem. Sci.*, 2014, **5**, 1368.
- (a) Y. Cui, Y. Yue, G. Qian and B. Chen, *Chem. Rev.*, 2012, **112**, 1126; (b) Y. Cui, B. Chen and G. Qian, *Coord. Chem. Rev.*, 2014, **273**, 76; (c) Y. Cui, T. Song, J. Yu, Y. Yang, Z. Wang and G. Qian, *Adv. Funct. Mater.*, 2015, **25**, 4796; (d) M.-J. Dong, M. Zhao, S. Ou, C. Zou and C.-D. Wu, *Angew. Chem., Int. Ed.*, 2014, **53**, 1575; (e) S.-R. Zhang, D.-Y. Du, J.-S. Qin, S.-L. Li, W.-W. He, Y.-Q. Lan and Z.-M. Su, *Inorg. Chem.*, 2014, **53**, 8105; (f) S.-R. Zhang, D.-Y. Du, K. Tan, J.-S. Qin, H.-Q. Dong, S.-L. Li, W.-W. He, Y.-Q. Lan, P. Shen and Z.-M. Su, *Chem.-Eur. J.*, 2013, **19**, 11279; (g) L.-H. Cao, F. Shi, W.-M. Zhang, S.-Q. Zang and T. C. W. Mak, *Chem.-Eur. J.*, 2015, DOI: 10.1002/chem.201501162.
- (a) M. Yoon, R. Srirambalaji and K. Kim, *Chem. Rev.*, 2012, **112**, 1196; (b) H. R. Moon, D.-W. Lim and M. P. Suh, *Chem. Soc. Rev.*, 2013, **42**, 1807; (c) J. Lee, O. K. Farha, J. Roberts, K. A. Scheidt, S. T. Nguyen and J. T. Hupp, *Chem. Soc. Rev.*, 2009, **38**, 1450; (d) J.-P. Ma, S.-Q. Wang, C.-W. Zhao, Y. Yu and Y.-B. Dong, *Chem. Mater.*, 2015, **27**, 3805.
- (a) Z. Hu, B. J. Deibert and J. Li, *Chem. Soc. Rev.*, 2014, **43**, 5815; (b) B. Chen, S. Xiang and G. Qian, *Acc. Chem. Res.*,

- 2010, **43**, 1115; (c) Y. Cui, F. Zhu, B. Chen and G. Qian, *Chem. Commun.*, 2015, **51**, 7420; (d) Y. Cui, H. Xu, Y. Yue, Z. Guo, J. Yu, Z. Chen, J. Gao, Y. Yang, G. Qian and B. Chen, *J. Am. Chem. Soc.*, 2012, **134**, 3979; (e) A. Lan, K. Li, H. Wu, D. H. Olson, T. J. Emge, W. Ki, M. Hong and J. Li, *Angew. Chem., Int. Ed.*, 2009, **48**, 2334; (f) S. Pramanik, C. Zheng, X. Zhang, T. J. Emge and J. Li, *J. Am. Chem. Soc.*, 2011, **133**, 4153; (g) Y.-S. Xue, Y. He, L. Zhou, F.-J. Chen, Y. Xu, H.-B. Du, X.-Z. You and B. Chen, *J. Mater. Chem. A*, 2013, **1**, 4525; (h) Y. Cui, R. Song, J. Yu, M. Liu, Z. Wang, C. Wu, Y. Yang, Z. Wang, B. Chen and G. Qian, *Adv. Mater.*, 2015, **27**, 1420; (i) S. Bhattacharyya, A. Chakraborty, K. Jayaramulu, A. Hazra and T. K. Maji, *Chem. Commun.*, 2014, **50**, 13567; (j) S.-R. Zhang, D.-Y. Du, J.-S. Qin, S.-J. Bao, S.-L. Li, W.-W. He, Y.-Q. Lan, P. Shen and Z.-M. Su, *Chem.-Eur. J.*, 2014, **20**, 3589.
- 6 F. A. A. Paz, J. Klinowski, S. M. F. Vilela, J. P. C. Tomé, J. A. S. Cavaleiro and J. Rocha, *Chem. Soc. Rev.*, 2012, **41**, 1088.
- 7 (a) G. Férey, C. Serre, T. Devic, G. Maurin, H. Jobic, P. L. Llewellyn, G. de Weireld, A. Vimont, M. Daturi and J.-S. Chang, *Chem. Soc. Rev.*, 2011, **40**, 550; (b) M. Kurmoo, *Chem. Soc. Rev.*, 2009, **38**, 1353; (c) N. Stock and S. Biswas, *Chem. Rev.*, 2011, **112**, 933; (d) S. Horike, D. Umeyama and S. Kitagawa, *Acc. Chem. Res.*, 2013, **46**, 2376; (e) A. Karmakar, A. V. Desai, B. Manna, B. Joarder and S. K. Ghosh, *Chem.-Eur. J.*, 2015, **21**, 7071; (f) X. Lian, D. Feng, Y.-P. Chen, T.-F. Liu, X. Wang and H.-C. Zhou, *Chem. Sci.*, 2015, DOI: 10.1039/c5sc02587g.
- 8 (a) S.-N. Zhao, X.-Z. Song, M. Zhu, X. Meng, L.-L. Wu, J. Feng, S.-Y. Song and H.-J. Zhang, *Chem.-Eur. J.*, 2015, **21**, 9748; (b) A. Schoedel, L. Wojtas, S. P. Kelley, R. D. Rogers, M. Eddaoudi and M. J. Zaworotko, *Angew. Chem., Int. Ed.*, 2011, **50**, 11421; (c) J. An, C. M. Shade, D. A. Changelis-Czegán, S. Petoud and N. L. Rosi, *J. Am. Chem. Soc.*, 2011, **133**, 122; (d) D. Chen, W. Shi and P. Cheng, *Chem. Commun.*, 2015, **51**, 370; (e) Z.-J. Zhang, W. Shi, Z. Niu, H.-H. Li, B. Zhao, P. Cheng, D.-Z. Liao and S.-P. Yan, *Chem. Commun.*, 2011, **47**, 6425.
- 9 (a) P.-F. Shi, B. Zhao, G. Xiong, Y.-L. Hou and P. Cheng, *Chem. Commun.*, 2012, **48**, 8231; (b) L. Shi, T. Wang, H. Zhang, K. Chang, X. Meng, H. Liu and J. Ye, *Advanced Science*, 2015, **2**, 1500006; (c) T. H. Noh, H. Lee, J. Jang and O.-S. Jung, *Angew. Chem., Int. Ed.*, 2015, **54**, 9284; (d) H. Fei, D. L. Rogow and S. R. J. Oliver, *J. Am. Chem. Soc.*, 2010, **132**, 7202; (e) J. Yu, Y. Cui, H. Xu, Y. Yang, Z. Wang, B. Chen and G. Qian, *Nat. Commun.*, 2013, **4**, 2719.
- 10 (a) L.-H. Cao, Y.-L. Wei, C. Ji, M.-L. Ma, S.-Q. Zang and T. C. W. Mak, *Chem.-Asian J.*, 2014, **9**, 3094; (b) Y. Zhu, Y.-M. Wang, S.-Y. Zhao, P. Liu, C. Wei, Y.-L. Wu, C.-K. Xia and J.-M. Xie, *Inorg. Chem.*, 2014, **53**, 7692; (c) Y.-X. Tan, Y. Zhang, Y.-P. He, Y.-J. Zheng and J. Zhang, *Inorg. Chem.*, 2014, **53**, 12973.
- 11 (a) F.-Y. Yi, W. Zhu, S. Dang, J.-P. Li, D. Wu, Y.-h. Li and Z.-M. Sun, *Chem. Commun.*, 2015, **51**, 3336; (b) S. Lin, Z. Song, G. Che, A. Ren, P. Li, C. Liu and J. Zhang, *Microporous Mesoporous Mater.*, 2014, **193**, 27; (c) C.-F. Zhang, L.-G. Qiu, F. Ke, Y.-J. Zhu, Y.-P. Yuan, G.-S. Xu and X. Jiang, *J. Mater. Chem. A*, 2013, **1**, 14329; (d) W. Fan, W. Gao, C. Zhang, W. W. Tjiu, J. S. Pan and T. X. Liu, *J. Mater. Chem.*, 2012, **22**, 25108.
- 12 S. H. Chen, J. Zhang, C. L. Zhang, Q. Y. Yue, Y. Li and C. Li, *Desalination*, 2010, **252**, 149.
- 13 (a) H.-L. Jiang, Y. Tatsu, Z.-H. Lu and Q. Xu, *J. Am. Chem. Soc.*, 2010, **132**, 5586; (b) F. Pu, X. Liu, B. Xu, J. Ren and X. Qu, *Chem.-Eur. J.*, 2012, **18**, 4322.
- 14 Y.-Q. Lan, H.-L. Jiang, S.-L. Li and Q. Xu, *Adv. Mater.*, 2011, **23**, 5015.
- 15 J.-S. Qin, S.-R. Zhang, D.-Y. Du, P. Shen, S.-J. Bao, Y.-Q. Lan and Z.-M. Su, *Chem.-Eur. J.*, 2014, **20**, 5625.
- 16 C.-Y. Sun, X.-L. Wang, C. Qin, J.-L. Jin, Z.-M. Su, P. Huang and K.-Z. Shao, *Chem.-Eur. J.*, 2013, **19**, 3639.
- 17 K. Selvi, S. Pattabhi and K. Kadirvelu, *Bioresour. Technol.*, 2001, **80**, 87.
- 18 (a) S. Paul, S. Goswami and A. Manna, *Dalton Trans.*, 2015, **44**, 11805; (b) Z. Zhou, M. Yu, H. Yang, K. Huang, F. Li, T. Yi and C. Huang, *Chem. Commun.*, 2008, 3387.
- 19 (a) X. Wang, T. M. Johnson and A. S. Ellis, *Geochim. Cosmochim. Acta*, 2015, **153**, 72; (b) T. A. Saleh, S. A. Haladu and S. A. Ali, *Chem. Eng. J.*, 2015, **269**, 9; (c) Y. Li, C. Liu and C. Chiou, *J. Colloid Interface Sci.*, 2004, **273**, 95.
- 20 (a) J. Dui, G. Zhu and S. Zhou, *ACS Appl. Mater. Interfaces*, 2013, **5**, 10081; (b) D. Park, Y.-S. Yun and J. M. Park, *Environ. Sci. Technol.*, 2004, **38**, 4860; (c) M. Bhaumik, H. J. Choi, M. P. Seopela, R. I. McCrindle and A. Maity, *Ind. Eng. Chem. Res.*, 2014, **53**, 1214.
- 21 (a) D. Kratochvil, P. Pimentel and B. Volesky, *Environ. Sci. Technol.*, 1998, **32**, 2693; (b) N. Shevchenko, V. Zaitsev and A. Walcarius, *Environ. Sci. Technol.*, 2008, **42**, 6922; (c) B. Li, D. Pan, J. Zheng, Y. Cheng, X. Ma, F. Huang and Z. Lin, *Langmuir*, 2008, **24**, 9630.
- 22 (a) B. Zhao, X.-Y. Chen, P. Cheng, D.-Z. Liao, S.-P. Yan and Z.-H. Jiang, *J. Am. Chem. Soc.*, 2004, **126**, 15394; (b) W. Liu, T. Jiao, Y. Li, Q. Liu, M. Tan, H. Wang and L. Wang, *J. Am. Chem. Soc.*, 2004, **126**, 2280; (c) Z. Hao, X. Song, M. Zhu, X. Meng, S. Zhao, S. Su, W. Yang, S. Song and H. Zhang, *J. Mater. Chem. A*, 2013, **1**, 11043; (d) X.-Z. Song, S.-Y. Song, S.-N. Zhao, Z.-M. Hao, M. Zhu, X. Meng, L.-L. Wu and H.-J. Zhang, *Adv. Funct. Mater.*, 2014, **24**, 4034; (e) Z. Hao, G. Yang, X. Song, M. Zhu, X. Meng, S. Zhao, S. Song and H. Zhang, *J. Mater. Chem. A*, 2014, **2**, 237; (f) B. Zhao, H.-L. Gao, X.-Y. Chen, P. Cheng, W. Shi, D.-Z. Liao, S.-P. Yan and Z.-H. Jiang, *Chem.-Eur. J.*, 2006, **12**, 149; (g) B. Zhao, X.-Y. Chen, Z. Chen, W. Shi, P. Cheng, S.-P. Yan and D.-Z. Liao, *Chem. Commun.*, 2009, 3113; (h) D. K. Singha and P. Mahata, *Inorg. Chem.*, 2015, **54**, 6373; (i) Z. Chen, Y. Sun, L. Zhang, D. Sun, F. Liu, Q. Meng, R. Wang and D. Sun, *Chem. Commun.*, 2013, **49**, 11557; (j) B. Liu, W.-P. Wu, L. Hou and Y.-Y. Wang, *Chem. Commun.*, 2014, **50**, 8731; (k) L. Wen, X. Zheng, K. Lv, C. Wang and X. Xu, *Inorg. Chem.*, 2015, **54**, 7133; (l) R.-M. Wen, S.-D. Han, G.-J. Ren, Z. Chang, Y.-W. Li and X.-H. Bu, *Dalton Trans.*, 2015, **44**, 10914.

- 23 V. A. Blatov, A. P. Shevchenko and D. M. Proserpio, *Cryst. Growth Des.*, 2014, **14**, 3576.
- 24 G.-S. Yang, Y.-Q. Lan, H.-Y. Zang, K.-Z. Shao, X.-L. Wang, Z.-M. Su and C.-J. Jiang, *CrystEngComm*, 2009, **11**, 274.
- 25 B. Adhikari, G. Palui and A. Banerjee, *Soft Matter*, 2009, **5**, 3452.
- 26 (a) G. Crini, *Bioresour. Technol.*, 2006, **97**, 1061; (b) Q.-R. Fang, G.-S. Zhu, Z. Jin, Y.-Y. Ji, J.-W. Ye, M. Xue, H. Yang, Y. Wang and S.-L. Qiu, *Angew. Chem., Int. Ed.*, 2007, **46**, 6638.
- 27 (a) A. A. Adeyemo, I. O. Adeoye and O. S. Bello, *Toxicol. Environ. Chem.*, 2012, **94**, 1846; (b) E. Haque, V. Lo, A. I. Minett, A. T. Harris and T. L. Church, *J. Mater. Chem. A*, 2014, **2**, 193; (c) M. Du, X. Wang, M. Chen, C.-P. Li, J.-Y. Tian, Z.-W. Wang and C.-S. Liu, *Chem.-Eur. J.*, 2015, **21**, 9713.
- 28 (a) J. Jia, F. Sun, T. Borjigin, H. Ren, T. Zhang, Z. Bian, L. Gao and G. Zhu, *Chem. Commun.*, 2012, **48**, 6010; (b) J. A. Greathouse, N. W. Ockwig, L. J. Criscenti, T. R. Guilinger, P. Pohl and M. D. Allendorf, *Phys. Chem. Chem. Phys.*, 2010, **12**, 12621; (c) F.-Y. Yi, J.-P. Li, D. Wu and Z.-M. Sun, *Chem.-Eur. J.*, 2015, **21**, 11475.
- 29 (a) S. Deng and Y. P. Ting, *Environ. Sci. Technol.*, 2005, **39**, 8490; (b) B. A. Manning, J. R. Kiser, H. Kwon and S. R. Kanel, *Environ. Sci. Technol.*, 2007, **41**, 586; (c) H.-K. Zhang, H. Lu, J. Wang, J.-T. Zhou and M. Sui, *Environ. Sci. Technol.*, 2014, **48**, 12876.
- 30 (a) G. M. Sheldrick, *SHELXS-97, Programs for X-ray Crystal Structure Solution*, University of Göttingen, Germany, 1997; (b) G. M. Sheldrick, *SHELXL-97, Programs for X-ray Crystal Structure Refinement*, University of Göttingen, Germany, 1997; (c) L. J. Farrugia, *WINGX, A Windows Program for Crystal Structure Analysis*, University of Glasgow, UK, 1988; (d) A. L. Spek, *J. Appl. Crystallogr.*, 2003, **36**, 7.